

General spin models from noncollinear spin density functional theory and spin-cluster expansion

Tomonori Tanaka* and Yoshihiro Gohda†

Department of Materials Science and Engineering, Institute of Science Tokyo, Yokohama 226-8501, Japan

(Dated: December 5, 2025)

We present a data-efficient framework for constructing general classical spin Hamiltonians from the spin-cluster expansion (SCE) combined with fully self-consistent noncollinear spin density functional theory (DFT). The key idea is to fit an SCE model to magnetic torques rather than to total energies. Because torques are site-resolved vectors, each configuration supplies many independent constraints, which makes the regression well conditioned and sharply reduces the number of DFT calculations needed, especially in large supercells. Applied to the B20-type chiral magnets $\text{Mn}_{1-x}\text{Fe}_x\text{Ge}$ and $\text{Fe}_{1-y}\text{Co}_y\text{Ge}$, the resulting models nonperturbatively extract the full pairwise exchange tensor (isotropic exchange, anisotropic symmetric exchange, and the Dzyaloshinskii–Moriya interaction) and predict helical spin period via a micromagnetic mapping. The composition trends and the divergence of the period near the chirality sign change are reproduced in line with experiments. Because the SCE framework is systematic, it also enables systematic analysis of interaction order; training on increasingly disordered spin configurations shows that the lowest-order model loses torque accuracy, whereas including higher-order interactions restores predictive power. These advances enable near-DFT-accurate spin models for finite-temperature magnetism and complex textures at modest data cost, while providing a systematic, extensible, and nonperturbative route to quantitative first-principles parameterization and predictive materials design. An open-source implementation is available as the Julia package, *Magestj.jl*.

I. INTRODUCTION

Recent advances in spintronic materials and technologies have been substantial, laying the groundwork for ultrafast, energy-efficient devices that exploit atomic-scale magnetic order and spin dynamics [1, 2]. In parallel, first-principles methods—especially density functional theory (DFT) [3, 4]—have become central to the understanding and design of magnetic and spintronic materials. However, fully *ab initio* treatments often reach practical limits when addressing finite-temperature magnetism and mesoscopic spin dynamics. Consequently, a broad class of statistical-mechanical models that coarse-grain the spin degrees of freedom has been developed [5–10]. A natural coarse-graining is to map the electronic system onto a classical spin model—a classical spin Hamiltonian that retains the orientations of local magnetic moments as degrees of freedom while integrating out charge and longitudinal fluctuations—so that the energy of a spin configuration is expressed through effective interaction parameters.

To leading order, the spin Hamiltonian in the vicinity of a locally stable spin configuration takes the form

$$E = \sum_{i,j,i \neq j} \sum_{\alpha,\beta} J_{ij}^{\alpha\beta} e_{i\alpha} e_{j\beta}, \quad (1)$$

where the Greek indices α, β denote Cartesian components, $e_{i\alpha}$ is the α component of the unit vector \hat{e}_i specifying the moment direction at site i , and $J_{ij}^{\alpha\beta}$ is the two-body exchange interaction tensor between sites i and j . This form is commonly sufficient to describe the immediate neighborhood of a locally stable magnetic state. However, when one seeks a unified description over a broader set of spin configurations, higher-order terms become necessary. For example,

temperature-dependent effective two-body isotropic terms (the Heisenberg interactions)—arising from the renormalization of higher-order interactions—are essential for modeling finite-temperature magnetic energetics [11]. Furthermore, recent studies suggest that higher-order interactions have an important role for the stabilization of complex spin structures, such as chiral spin textures and skyrmions [12–14]. Accordingly, the importance of establishing quantitative methods to evaluate higher-order interactions is increasingly pronounced.

Systematically extending Eq. (1) to include higher-order terms in a Taylor-series fashion is challenging because the customary basis functions are not orthogonal. This lack of orthogonality leads to ill-conditioned regressions and, under crystal symmetry, introduces cumbersome constraints among model parameters. As a theoretically rigorous alternative, Drautz and Fähnle proposed the spin-cluster expansion (SCE) method [15, 16]. Within SCE, the magnetic energy is a function of the unit vectors \hat{e}_i representing a spin direction at site i :

$$E_{\text{SCE}}(\{\hat{e}_i\}) = J_0 + \sum_{\mathcal{C}} \sum_{l>0} \sum_{\mathbf{m}} J_{\mathcal{C}l\mathbf{m}} \Phi_{\mathcal{C}l\mathbf{m}}(\{\hat{e}_i\}), \quad (2)$$

where J_0 is a reference energy, \mathcal{C} is the cluster index, $J_{\mathcal{C}l\mathbf{m}}$ are the SCE coefficients, and $\Phi_{\mathcal{C}l\mathbf{m}}$ is a basis function formed by products of spherical harmonics Y_{lm} ,

$$\Phi_{\mathcal{C}l\mathbf{m}}(\{\hat{e}_i\}) = (\sqrt{4\pi})^{n_{\mathcal{C}}} \prod_{i=1}^{n_{\mathcal{C}}} Y_{l_i m_i}(\hat{e}_i), \quad (3)$$

with $n_{\mathcal{C}}$ the number of sites in cluster \mathcal{C} and $\mathbf{l} = (l_1, \dots, l_{n_{\mathcal{C}}})$, $\mathbf{m} = (m_1, \dots, m_{n_{\mathcal{C}}})$. In spherical coordinates (θ, ϕ) ,

$$Y_{lm}(\theta, \phi) = (-1)^m \sqrt{\frac{2l+1}{4\pi} \frac{(l-m)!}{(l+m)!}} P_{lm}(\cos \theta) e^{im\phi}, \quad (4)$$

where P_{lm} are the associated Legendre polynomials related to

* tanaka.t.da74@m.isct.ac.jp

† gohda@mct.isct.ac.jp

the Legendre polynomials P_l via

$$P_{lm}(x) = (1 - x^2)^{m/2} \frac{d^m P_l(x)}{dx^m}. \quad (5)$$

The set Φ_{Clm} , together with the constant term, forms an orthogonal and complete basis set [15]. By increasing the maximum degree l and the cluster size, the model can be systematically improved.

In principle, the SCE coefficients J_{Clm} can be obtained by regressing to constrained noncollinear-spin DFT total energies, as shown in earlier SCE work [17] and by analogy with the cluster expansion for substitutional alloys [18]. In practice, however, magnetic interactions operate on energy scales far smaller than chemical interactions in alloys, which demands higher precision from DFT. Moreover, whereas alloy variables are discrete, spin orientations are continuous, so the configuration space is vast; fits that rely only on total energies therefore require prohibitively many samples to reproduce the energy landscape with accuracy. A practical solution is to augment the regression with information beyond total energies—namely, derivatives with respect to spin orientations (magnetic torques). The use of derivatives is well established elsewhere: in finite-displacement phonon calculations one fits DFT-computed forces to build Taylor-expanded potentials [19, 20], and modern machine-learning interatomic potentials train on both energies and forces [21]. In magnetism, analogous strategies—fitting to magnetic torques from noncollinear-spin DFT—have been applied primarily to some spin models [22–25]. Integrating these ideas into the SCE framework yields a data-efficient and systematic route derivation of general spin models.

In this work, we present an efficient and scalable spin-cluster expansion (SCE) framework fitted to magnetic torque data. Unlike earlier SCE implementations [17, 26, 27], our approach is able to treat spin–orbit coupling (SOC) explicitly, which breaks global spin rotational invariance and necessitates anisotropic terms in spin models. This enables non-perturbative evaluation of arbitrary anisotropic terms in the spin Hamiltonian, including single-ion anisotropy, symmetric exchange anisotropy, and the antisymmetric Dzyaloshinskii–Moriya interaction (DMI). The paper is organized as follows. Section II A introduces a formulation in real spherical harmonics that ensures a real-valued energy and streamlines SOC treatment. Building on this, Section II B derives symmetry-adapted basis functions via a projection operator to enforce crystal-symmetry constraints on SCE coefficients. Section II C then describes the torque-fitted regression scheme, and Section II D presents the real harmonics and their derivatives on the unit sphere in Cartesian coordinates used in the torque-fitted regression. In Sec. II E, we describe a simple mean-field-based sampling scheme that generates temperature-controlled spin configurations to serve as training data for constructing the SCE model. We apply our method to B20-type chiral compounds $\text{Mn}_{1-x}\text{Fe}_x\text{Ge}$ and $\text{Fe}_{1-y}\text{Co}_y\text{Ge}$ (Section II F) as demonstrations. First, we show that the torque-fitted regression drastically reduces the number of DFT data points needed to construct an SCE model. We then use the resulting models to evaluate the full exchange tensor (consisting

of isotropic exchange, anisotropic symmetric exchange, and DMI), extract the helical period via micromagnetic models, and reproduce the experimentally observed divergence of the period as a function of composition. Finally, by increasing the sampling temperature to generate more strongly fluctuating spin configurations, we assess the validity of a lowest-order spin Hamiltonian and observe reduced predictive accuracy for torque predictions, indicating that higher-order interactions are required at elevated temperatures. The paper concludes with Section III, which summarizes the main findings and outlines future directions. Our implementation is released as an open-source Julia package, *Magesty.jl*.

II. RESULTS

A. Spin-cluster expansion with real spherical harmonics

In the original implementation of SCE [15, 16], complex spherical harmonics were employed. Subsequently, Ref. [26] ensured a real-valued energy by assuming global spin rotation invariance (i.e., neglecting SOC) together with time-reversal symmetry. When SOC is included, however, using complex spherical harmonics requires explicit constraints on the SCE coefficients to guarantee that the total energy remains real. To avoid this bookkeeping and to simplify SOC implementations, we work with real spherical harmonics.

The real spherical harmonics Z_{lm} are defined by

$$Z_{lm} = \begin{cases} \frac{(-1)^m}{\sqrt{2}}(Y_{lm} + (-1)^m Y_{l\bar{m}}), & m > 0, \\ Y_{l0}, & m = 0, \\ \frac{(-1)^m}{i\sqrt{2}}(Y_{l|m|} - (-1)^{|m|} Y_{l|\bar{m}|}), & m < 0, \end{cases} \quad (6)$$

where $\bar{m} \equiv -m$ and $|m| \equiv -|m|$. Collecting the harmonics for a fixed l into column vectors ordered by increasing m as $\mathbf{Z}_l \equiv (Z_{l\bar{l}}, \dots, Z_{ll})^\top$ and $\mathbf{Y}_l \equiv (Y_{l\bar{l}}, \dots, Y_{ll})^\top$, (with $(\cdot)^\top$ denoting transpose), the transformation in Eq. (6) can be written compactly as

$$\mathbf{Z}_l = \mathbf{C}_l \mathbf{Y}_l, \quad (7)$$

where \mathbf{C}_l is a unitary matrix. An explicit form is

$$\mathbf{C}_l = \frac{1}{\sqrt{2}} \begin{pmatrix} i & 0 & \cdots & 0 & \cdots & 0 & -i(-1)^l \\ 0 & i & \cdots & 0 & \cdots & -i(-1)^{l-1} & 0 \\ \vdots & \vdots & \ddots & \vdots & \ddots & \vdots & \vdots \\ 0 & 0 & \cdots & \sqrt{2} & \cdots & 0 & 0 \\ \vdots & \vdots & \ddots & \vdots & \ddots & \vdots & \vdots \\ 0 & 1 & \cdots & 0 & \cdots & (-1)^{l-1} & 0 \\ 1 & 0 & \cdots & 0 & \cdots & 0 & (-1)^l \end{pmatrix}, \quad (8)$$

with construction rules given in Ref. [28].

The SCE written in terms of real spherical harmonics is obtained by replacing the complex-harmonic basis Φ_{clm} in Eq. (2) as

$$E_{\text{SCE}}(\{\hat{e}_i\}) = J_0 + \sum_c \sum_{l>0} \sum_m J_{clm} \Psi_{clm}(\{\hat{e}_i\}), \quad (9)$$

$$\Psi_{clm}(\{\hat{e}_i\}) = (\sqrt{4\pi})^{n_c} \prod_{i=1}^{n_c} Z_{l_i m_i}(\hat{e}_i). \quad (10)$$

The prefactor $(\sqrt{4\pi})^{n_c}$ is chosen such that the cluster basis functions are orthonormal with respect to the scalar product

$$\langle \Psi_{clm} | \Psi_{c'l'm'} \rangle \equiv \frac{1}{(4\pi)^N} \int d\hat{e}_1 \cdots \int d\hat{e}_N \Psi_{clm} \Psi_{c'l'm'}, \quad (11)$$

where N is the total number of sites and $\int d\hat{e}_i$ denotes integration over the unit sphere [15, 26]. One then obtains the orthonormality relation

$$\langle \Psi_{clm} | \Psi_{c'l'm'} \rangle = \delta_{cc'} \delta_{ll'} \delta_{mm'}. \quad (12)$$

For products over multiple sites, it is convenient to use Kronecker products. Define the block vectors

$$\mathbf{Z}_l \equiv \bigotimes_{i=1}^{n_c} \mathbf{Z}_{l_i}, \quad \mathbf{Y}_l \equiv \bigotimes_{i=1}^{n_c} \mathbf{Y}_{l_i}, \quad (13)$$

and the corresponding transformation

$$\mathbf{C}_l \equiv \bigotimes_{i=1}^{n_c} \mathbf{C}_{l_i} = \mathbf{C}_{l_1} \otimes \mathbf{C}_{l_2} \otimes \cdots \otimes \mathbf{C}_{l_{n_c}}. \quad (14)$$

Then the complex-to-real mapping factorizes as

$$\mathbf{Z}_l = \mathbf{C}_l \mathbf{Y}_l. \quad (15)$$

B. Construction of symmetry-adapted basis functions

A system that possesses a symmetry represented by a group G must have an energy that is invariant under every symmetry operation in G . In the framework of the SCE, this invariance can be achieved by constructing new basis functions as appropriate linear combinations of original ones (Ψ_{clm}), such that they form a basis for the identity representation of the group G . For this purpose, we apply a group-theoretical projection-operator method. The essential part of constructing the projection-operator method in the context of the SCE has already been explained in Ref. [27]. The key difference from the approach in Ref. [27] is that while they assume global spin-rotational symmetry and time-reversal symmetry to ensure real-valuedness of the model, we do not impose the former symmetry. Instead, we employ real spherical harmonics to ensure that the SCE model remains real-valued; although either set of spherical harmonics is equivalent in principle, using the real form offers the practical advantage that both the basis functions and the SCE coefficients remain strictly real in the

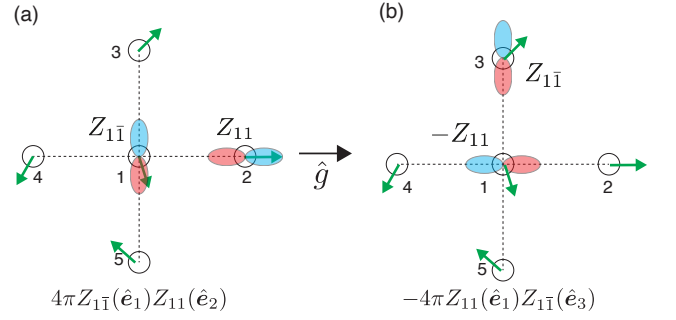


FIG. 1. Example of a symmetry operation \hat{g} acting on a basis function, where \hat{g} is a counterclockwise rotation of 90° . The circles and accompanying arrows represent atoms and spin directions, respectively. (a) Original function $\Psi_{clm} = 4\pi Z_{11}(\hat{e}_1) Z_{11}(\hat{e}_2)$. (b) Transformed function $\hat{g}\Psi_{clm} = -4\pi Z_{11}(\hat{e}_1) Z_{11}(\hat{e}_3)$. For clarity, color images of p_x (corresponding to Z_{11}) and p_y (corresponding to $Z_{1\bar{1}}$) orbitals are also shown.

implementation. Below, we describe the projection-operator approach for the case using real spherical harmonics.

We consider a paramagnetic group \bar{G}_0 which consists of a space group G_0 and the time-reversal operation \hat{T} as

$$\bar{G}_0 = G_0 + \hat{T}G_0, \quad (16)$$

where $\hat{T}G_0$ is the set formed by the product of the time-reversal operation \hat{T} and the symmetry operations belonging to the space group G_0 . Note that we do not impose any symmetry of a specific magnetic order; magnetic space-group symmetries are not considered. Magnetic space groups may emerge when the original spin Hamiltonian is approximated by an effective field Hamiltonian (e.g., by mean-field approximation), but they do not represent the fundamental symmetry group that the original spin model is required to obey. The projection operator of the identity irreducible representation \hat{P}_{id} is defined as follows:

$$\hat{P}_{\text{id}} = \frac{1}{|\bar{G}_0|} \left(\sum_{\hat{g} \in G_0} \hat{g} + \sum_{\hat{g} \in G_0} \hat{T}\hat{g} \right), \quad (17)$$

where \hat{g} is the crystal-symmetry operation in G_0 , and $|\bar{G}_0|$ is the order of group \bar{G}_0 . The desired symmetry-adapted basis functions are eigenfunctions of the matrix represented as

$$\langle \Psi_{c'l'm'} | \hat{P}_{\text{id}} | \Psi_{clm} \rangle. \quad (18)$$

We decompose \hat{g} into two commuting operations: (i) a permutation of site labels \hat{g}_{site} induced by the mapping of atomic positions, and (ii) a basis rotation \hat{g}_{rot} acting on spherical harmonics at fixed arguments (i.e., we rotate the *basis functions* rather than the arguments \hat{e}_i). An example of \hat{g} acting on a basis function Ψ_{clm} is shown in Figs. 1(a) and (b). From this example, the effect of the site mapping is clear; it merely permutes the site indices in the basis functions. Accordingly, in what follows we focus on how the point-symmetry (basis-rotation) part \hat{g}_{rot} acts on the basis functions, and we omit the explicit site-permutation part \hat{g}_{site} for conciseness. The

matrix form of the first term in the right-hand side of Eq. (17) is written as

$$\begin{aligned} \frac{1}{|G_0|} \sum_{\hat{g} \in G_0} \hat{g} &\doteq \frac{1}{|G_0|} \sum_{\hat{g} \in G_0} \langle \Psi_{c'l'm'} | \hat{g} | \Psi_{clm} \rangle \\ &= \frac{1}{|G_0|} \sum_{\hat{g} \in G_0} \Delta_l(\hat{g}). \end{aligned} \quad (19)$$

Since the basis functions consist of the Kronecker product as Eq. (15), $\Delta_l(\hat{g})$ is written as

$$\Delta_l(\hat{g}) = \bigotimes_{i=1}^{n_c} \Delta_{l_i}(\hat{g}), \quad (20)$$

where $\Delta_{l_i}(\hat{g})$ is the matrix representation of the symmetry operation \hat{g} acting on Z_{l_i} . If the point-symmetry operation part of \hat{g} corresponds to a proper rotation \hat{R} , i.e., the determinant of the transform matrix equals 1, $\Delta_l(\hat{g})$ can be obtained from the Wigner D -matrix and C_l in Eq. (8) as follows [28]:

$$\begin{aligned} \Delta_{lmm'}(\hat{R}) &= \langle Z_{lm} | \hat{R} | Z_{lm'} \rangle \\ &= \sum_{m''m'''} C_{lm''m'''}^* C_{lm'm'''} \langle Y_{lm''} | \hat{R} | Y_{lm'''} \rangle \\ &= \sum_{m''m'''} C_{lm''m'''}^* D_{lm''m'''}(\hat{R}) C_{lm'm'''} \end{aligned} \quad (21)$$

Therefore, Δ_l can be expressed as

$$\Delta_l(\hat{R}) = C_l^* \mathbf{D}_l(\hat{R}) C_l^T, \quad (22)$$

where $\mathbf{D}_l(\hat{R})$ is the Kronecker product of the Wigner D -matrices in the same manner as in Eq. (20). Even for improper rotations \hat{R}' (with determinant -1), the matrix representations are obtained by noting that any \hat{R}' can be written as the product of a corresponding proper rotation \hat{R} and spatial inversion \hat{I} , i.e., $\hat{R}' = \hat{R}\hat{I} = \hat{I}\hat{R}$. Because spin is an axial (pseudovector) quantity, spatial inversion does not reverse its direction; it merely permutes the site (cluster) indices. Hence,

$$\hat{I} \Psi_{clm} = \Psi_{c'l'm}, \quad (23)$$

where $C' \equiv \hat{I}(C)$ denotes the image of the cluster under inversion. Therefore, the matrix representation of any improper rotation $\hat{R}' = \hat{R}\hat{I}$ can be obtained in the same manner as for proper rotations (up to the index permutation induced by \hat{I}).

Finally, the time-reversal operator \hat{T} flips the spin direction, $\hat{T} \hat{e}_i \mapsto -\hat{e}_i$. Therefore,

$$\hat{T} \Psi_{clm}(\{\hat{e}_i\}) = (-1)^{\sum_{i=1}^{n_c} l_i} \Psi_{clm}(\{\hat{e}_i\}). \quad (24)$$

It follows that only cluster terms with an even $\sum_{i=1}^{n_c} l_i$ are \hat{T} -even and therefore allowed as a time-reversal-invariant function, whereas terms with an odd $\sum_{i=1}^{n_c} l_i$ are \hat{T} -odd and thus excluded [26]. Combining this with the spatial symmetry operations, we can construct the projector onto the identity irreducible representation. The symmetry-adapted basis functions are the eigenfunctions of \hat{P}_{id} with eigenvalue 1 [28].

C. Estimation of SCE coefficients utilizing local magnetic torques

We estimate the SCE coefficients using effective magnetic torques obtained from constrained noncollinear-spin DFT [29]. The torque at atomic site i , T_i , is defined as the energy gradient on the unit sphere cast into a physical torque,

$$\mathbf{T}_{\text{DFT},i} \equiv -\hat{e}_i \times (-\nabla_{\hat{e}_i} E_{\text{DFT}}) = -\mathbf{M}_i \times \mathbf{B}_i, \quad (25)$$

where E_{DFT} is the total energy, $\mathbf{M}_i = M_i \hat{e}_i$ is the local magnetic moment, and \mathbf{B}_i is a site-averaged effective magnetic field. At self-consistency, \mathbf{B}_i is transverse to \hat{e}_i and equal in magnitude and opposite in direction to the constraining field [29]. Hence both sides of $-\nabla_{\hat{e}_i} E_{\text{DFT}} = M_i \mathbf{B}_i$ lie in the tangent plane at \hat{e}_i . For completeness, the gradient on the unit sphere with respect to $\hat{e}_i = (e_{ix}, e_{iy}, e_{iz})$ is

$$\nabla_{\hat{e}_i} f(\hat{e}_i) = \nabla f(\hat{e}_i) - (\hat{e}_i \cdot \nabla f(\hat{e}_i)) \hat{e}_i, \quad (26)$$

$$\nabla f(\hat{e}_i) = \frac{\partial f}{\partial e_{ix}} \mathbf{i} + \frac{\partial f}{\partial e_{iy}} \mathbf{j} + \frac{\partial f}{\partial e_{iz}} \mathbf{k}, \quad (27)$$

with $\mathbf{i}, \mathbf{j}, \mathbf{k}$ the Cartesian unit vectors.

Let \mathbf{J} be the N_l -vector collecting the irreducible, symmetry-adapted SCE coefficients (excluding J_0). The SCE energy can be written as

$$E_{\text{SCE}}(\{\hat{e}_i\}) = J_0 + \mathbf{u}^T \mathbf{J}, \quad (28)$$

where $\mathbf{u} = \partial E_{\text{SCE}}(\{\hat{e}_i\}) / \partial \mathbf{J}$ is a vector function of the spin directions. The corresponding torque is

$$\mathbf{T}_{\text{SCE},i} = -\hat{e}_i \times (-\nabla_{\hat{e}_i} E_{\text{SCE}}) = -\hat{e}_i \times \left[-(\nabla_{\hat{e}_i} \mathbf{u}^T) \mathbf{J} \right]. \quad (29)$$

Collecting all sites, this becomes the linear relation

$$\mathbf{T}_{\text{SCE}} = \mathbf{A} \mathbf{J}, \quad (30)$$

where $\mathbf{T}_{\text{SCE}} \in \mathbb{R}^{3N_a}$ and $\mathbf{A} \in \mathbb{R}^{3N_a \times N_l}$ has block rows

$$\mathbf{A} = \begin{pmatrix} \hat{\mathbf{e}}_1 \times (\nabla_{\hat{\mathbf{e}}_1} u_1) & \hat{\mathbf{e}}_1 \times (\nabla_{\hat{\mathbf{e}}_1} u_2) & \cdots & \hat{\mathbf{e}}_1 \times (\nabla_{\hat{\mathbf{e}}_1} u_{N_I}) \\ \hat{\mathbf{e}}_2 \times (\nabla_{\hat{\mathbf{e}}_2} u_1) & \hat{\mathbf{e}}_2 \times (\nabla_{\hat{\mathbf{e}}_2} u_2) & \cdots & \hat{\mathbf{e}}_2 \times (\nabla_{\hat{\mathbf{e}}_2} u_{N_I}) \\ \vdots & \vdots & \ddots & \vdots \\ \hat{\mathbf{e}}_{N_a} \times (\nabla_{\hat{\mathbf{e}}_{N_a}} u_1) & \hat{\mathbf{e}}_{N_a} \times (\nabla_{\hat{\mathbf{e}}_{N_a}} u_2) & \cdots & \hat{\mathbf{e}}_{N_a} \times (\nabla_{\hat{\mathbf{e}}_{N_a}} u_{N_I}) \end{pmatrix}.$$

For N_{data} spin configurations, we stack the site torques and design matrices:

$$\tilde{\mathbf{T}}_{\text{SCE}} = \tilde{\mathbf{A}} \mathbf{J}, \quad \tilde{\mathbf{T}} \equiv \begin{pmatrix} \mathbf{T}_1 \\ \mathbf{T}_2 \\ \vdots \\ \mathbf{T}_{N_{\text{data}}} \end{pmatrix}, \quad \tilde{\mathbf{A}} \equiv \begin{pmatrix} \mathbf{A}_1 \\ \mathbf{A}_2 \\ \vdots \\ \mathbf{A}_{N_{\text{data}}} \end{pmatrix}. \quad (31)$$

Identifying $\tilde{\mathbf{T}}_{\text{SCE}}$ with the DFT torques $\tilde{\mathbf{T}}_{\text{DFT}}$, we determine \mathbf{J} by minimizing the squared Frobenius-norm loss

$$\mathcal{L} = \|\tilde{\mathbf{T}}_{\text{DFT}} - \tilde{\mathbf{T}}_{\text{SCE}}\|_2^2. \quad (32)$$

When the system is well determined, \mathbf{J} is determined as $\mathbf{J} = (\tilde{\mathbf{A}}^\top \tilde{\mathbf{A}})^{-1} \tilde{\mathbf{A}}^\top \tilde{\mathbf{T}}_{\text{DFT}}$.

D. Real spherical harmonics represented as polynomials of Cartesian coordinates

In torque-fitted regression formalism, we must evaluate gradients of the spherical harmonics with respect to the unit vec-

tor, cf. Eq. (29). Differentiation in spherical coordinates (θ, ϕ) is numerically ill-conditioned near the poles ($\sin \theta \rightarrow 0$). To avoid these coordinate singularities, we represent the spherical harmonics as polynomials in the Cartesian components of the unit vector, which yields well-behaved analytic derivatives via $\partial/\partial e_x$, $\partial/\partial e_y$, and $\partial/\partial e_z$. The gradient of the complex spherical harmonics with respect to the unit vector was already derived in Ref. [30]. Here, we present expressions for the gradients of the real spherical harmonics in their Cartesian-polynomial form. See also the Supplementary Information for details of the derivations.

The complex spherical harmonics Y_{lm} for $m \geq 0$ can be written in Cartesian coordinates as follows [30]:

$$Y_{lm}(\hat{\mathbf{e}}_i) = (e_{ix} + ie_{iy})^m \bar{P}_{lm}(e_{iz}), \quad (33)$$

$$\bar{P}_{lm}(e_{iz}) = (-1)^m \sqrt{\frac{2l+1}{4\pi}} \cdot \frac{(l-m)!}{(l+m)!} \frac{d^m}{de_{iz}^m} P_l(e_{iz}). \quad (34)$$

For $m < 0$, the corresponding expressions follow from the relation $Y_{l\bar{m}} = (-1)^{|m|} Y_{l|m|}^*$. Hereafter, we omit the arguments $\hat{\mathbf{e}}_i$ and the spin index i when not explicitly required. From Eqs. (6), (33), and (34) we obtain the real spherical harmonics in Cartesian coordinates as follows:

$$Z_{lm} = \begin{cases} (-1)^m \sqrt{2} \bar{P}_{lm}(e_z) \sum_{k=0}^{[m/2]} (-1)^k \binom{m}{2k} e_x^{m-2k} e_y^{2k}, & m > 0 \\ \bar{P}_{l0}(e_z), & m = 0, \\ (-1)^m \sqrt{2} \bar{P}_{l|m|}(e_z) \sum_{k=0}^{[(|m|-1)/2]} (-1)^k \binom{|m|}{2k+1} e_x^{|m|-(2k+1)} e_y^{2k+1}, & m < 0 \end{cases} \quad (35)$$

where $[x]$ denotes the floor function (i.e., the largest integer less than or equal to x), and $\binom{m}{k}$ is the binomial coefficient.

The gradient of the real spherical harmonics with respect to the unit vector $\hat{\mathbf{e}}$ can be derived using Eqs. (26) and (27) as follows:

$$\nabla_{\hat{\mathbf{e}}} Z_{lm}(\hat{\mathbf{e}}) = \nabla Z_{lm}(\hat{\mathbf{e}}) - (\hat{\mathbf{e}} \cdot \nabla Z_{lm}(\hat{\mathbf{e}})) \hat{\mathbf{e}}, \quad (36)$$

$$\nabla Z_{lm}(\hat{\mathbf{e}}) = \frac{\partial Z_{lm}}{\partial e_x} \mathbf{i} + \frac{\partial Z_{lm}}{\partial e_y} \mathbf{j} + \frac{\partial Z_{lm}}{\partial e_z} \mathbf{k}. \quad (37)$$

The partial derivatives $\partial Z_{lm}/\partial e_\alpha$ ($\alpha \in x, y, z$) for $m > 0$ are given by:

$$\frac{\partial Z_{lm}}{\partial e_x} = (-1)^m \sqrt{2m} \bar{P}_{lm}(e_z) \sum_{k=0}^{[(m-1)/2]} (-1)^k \binom{m-1}{2k} e_x^{m-1-2k} e_y^{2k}, \quad (38)$$

$$\frac{\partial Z_{lm}}{\partial e_y} = -\frac{\partial Z_{l\bar{m}}}{\partial e_x}, \quad (39)$$

$$\frac{\partial Z_{lm}}{\partial e_z} = (-1)^m \sqrt{2} \left(\frac{d\bar{P}_{lm}(e_z)}{de_z} \right) \sum_{k=0}^{[m/2]} (-1)^k \binom{m}{2k} e_x^{m-2k} e_y^{2k}. \quad (40)$$

For $m = 0$,

$$\frac{\partial Z_{l0}}{\partial e_x} = \frac{\partial Z_{l0}}{\partial e_y} = 0, \quad (41)$$

$$\frac{\partial Z_{l0}}{\partial e_z} = \frac{d\bar{P}_{l0}(e_z)}{de_z}. \quad (42)$$

For $m < 0$,

$$\frac{\partial Z_{lm}}{\partial e_x} = (-1)^m \sqrt{2} |m| \bar{P}_{l|m|}(e_z) \sum_{k=0}^{[(|m|-2)/2]} (-1)^k \binom{|m|-1}{2k+1} e_x^{|m|-2-2k} e_y^{2k+1}, \quad (43)$$

$$\frac{\partial Z_{lm}}{\partial e_y} = \frac{\partial Z_{l|m|}}{\partial e_x}, \quad (44)$$

$$\frac{\partial Z_{lm}}{\partial e_z} = (-1)^m \sqrt{2} \left(\frac{d\bar{P}_{l|m|}(e_z)}{de_z} \right) \sum_{k=0}^{[(|m|-1)/2]} (-1)^k \binom{|m|}{2k+1} e_x^{|m|-2k-1} e_y^{2k+1}. \quad (45)$$

We adopt the convention that whenever the upper limit of a summation is smaller than the lower limit, the sum is taken to be empty and hence evaluates to zero. In particular, in Eq. (43) the upper limit $[(|m|-2)/2]$ is negative for $|m| = 1$, so the sum vanishes and $\partial Z_{l\bar{1}}/\partial e_x = 0$. Based on the above expressions, we can evaluate the gradients of the SCE basis functions for a given spin configuration.

E. Sampling method based on the mean-field approximation

Constructing an SCE model requires sampling spin configurations that adequately span the magnetic states of interest. In general, building a model that reproduces energies across arbitrary magnetic states with high accuracy within a realistic computational budget will demand sophisticated strategies, which we defer to future work. In the applications presented below, we instead assume that the relevant magnetic states are known *a priori*. For this setting, we employ a practical mean-field-based sampling scheme for the Heisenberg model that efficiently generates spin configurations representative of the target states [11, 31, 32]. Within the mean-field Heisenberg model single-site orientational probability $P(\hat{e}_i)$ takes the von Mises–Fisher form,

$$P(\hat{e}_i) = \frac{3m/\tau}{4\pi \sinh(3m/\tau)} \exp\left(\frac{3m\hat{e} \cdot \hat{e}_i}{\tau}\right), \quad (46)$$

where $\mathbf{m} = \langle \hat{e} \rangle = m\hat{e}$ is the site-independent thermal average of the spin and $\tau = T/T_c^{\text{MFA}}$ is a reduced temperature (T is the temperature and T_c^{MFA} is the mean-field critical temperature). The parameters m and τ are self-consistently related; fixing one automatically determines the other. Therefore, by choosing τ , one can sample \hat{e}_i from this distribution to generate spin configurations representative of the target magnetic disorder within the mean-field approximation. Please refer to Ref. [11] for the derivation and further details.

F. Application to B20-type $\text{Mn}_{1-x}\text{Fe}_x\text{Ge}$ and $\text{Fe}_{1-y}\text{Co}_y\text{Ge}$

B20-type chiral magnetic compounds $\text{Mn}_{1-x}\text{Fe}_x\text{Ge}$ and $\text{Fe}_{1-y}\text{Co}_y\text{Ge}$ exhibit helical spin structures [33–43]. From a theoretical standpoint, their spin–orbit coupling is moderate, so they serve as testbeds for developing DFT-based methods to evaluate the Dzyaloshinskii–Moriya interaction (DMI) [44–47]. Here, we apply the SCE method to the B20-type compounds and examine the applicability via the evaluation of exchange interaction, DMI, and helical spin period.

We used a $2 \times 2 \times 2$ cubic supercell including 64 atoms with experimental crystallographic structural parameters of FeGe [34] and constructed an SCE model using spin configurations sampled from states close to the ferromagnetic state. Sampling is performed using the mean-field distribution in Eq. (46) at the scaled temperature $\tau = 0.1$. As the SCE model, we consider

the constant term and two-body interactions with the lowest l -index as

$$E_{\text{SCE}} = J_0 + \sum_{i \neq j} \sum_{l_i, l_j=1}^{l_{\max}=1} \sum_{m_i=-l_i}^{l_i} \sum_{m_j=-l_j}^{l_j} J_{ijlm} Z_{l_i m_i}(\hat{e}_i) Z_{l_j m_j}(\hat{e}_j). \quad (47)$$

We included all possible two-body pairs (Fe–Fe, Fe–Ge, and Ge–Ge). By constructing symmetry-adapted basis functions, the number of independent SCE coefficients excluding the constant term resulted in 324. This SCE model is equivalent to the generalized Heisenberg model consisting of the isotropic exchange term, DMI, and anisotropic symmetric interaction term as

$$E = - \sum_{i,j,i \neq j} J_{ij} \hat{e}_i \cdot \hat{e}_j + \sum_{i,j,i \neq j} \mathbf{D}_{ij} \cdot (\hat{e}_i \times \hat{e}_j) + \sum_{i,j,i \neq j} \hat{e}_i^T \mathbf{\Gamma}_{ij} \hat{e}_j, \quad (48)$$

where J_{ij} is the isotropic exchange parameter, \mathbf{D}_{ij} is the DMI vector, and $\mathbf{\Gamma}_{ij}$ is the anisotropic symmetric interaction matrix with conditions $\mathbf{\Gamma}_{ij} = \mathbf{\Gamma}_{ij}^T$ and $\text{tr}[\mathbf{\Gamma}_{ij}] = 0$. The conversion rule from SCE coefficients to J_{ij} , \mathbf{D}_{ij} , and $\mathbf{\Gamma}_{ij}$ is explained in Sec. IV B.

We first demonstrate that torque-fitted regression reduces the number of required DFT data points. Figure 2 plots the convergence of the first-nearest-neighbor Fe–Fe exchange coupling J_{01} and the magnitude of the DMI vector $|\mathbf{D}_{01}|$ versus the number of DFT data points for the torque-fitted and energy-fitted approaches. In the conventional energy-fitted regression, both parameters begin to stabilize around $N_{\text{data}} = 210$, which is the number of independent parameters in the SCE model. In contrast, the torque-fitted regression requires far fewer DFT data points for parameter convergence, because each configuration provides $3N_a$ targets (the x , y , and z torque components on each atom) rather than a single scalar energy; thus, by a simple calculation, the number of configurations needed scales as $\sim 1/(3N_a)$ relative to the energy-fitted case— $1/192$ in the present system ($N_a = 64$). Consequently, convergence is achieved with only a small number of data points. Collectively, these reductions make the SCE model practical and data-efficient when parameterized via torque-fitted regression. As the supercell size grows (and thus N_a increases), the relative efficiency over the energy-fitted approach becomes even more pronounced, making torque-fitted parameterization especially advantageous for larger supercells.

Next, we analyze the helical spin structures of $\text{Mn}_{1-x}\text{Fe}_x\text{Ge}$ and $\text{Fe}_{1-y}\text{Co}_y\text{Ge}$. Following Refs. [45–48], we employ a micromagnetic energy functional derived from Eq. (48) together with the B20 crystal geometry. Exploiting the cubic symmetry of the B20 structure, the energy functional can be written as

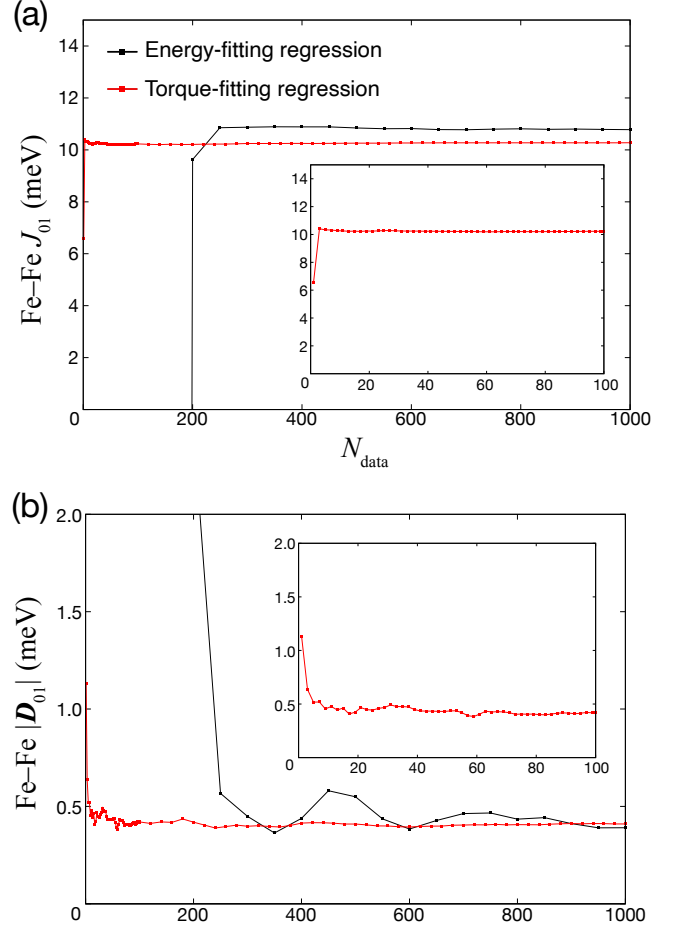


FIG. 2. Comparison of the convergence with respect to the number of DFT data points N_{data} for energy-fitted (black) and torque-fitted (red) regression. Panels (a) and (b) show the first-nearest-neighbor Fe–Fe exchange coupling J_{01} and the magnitude of the DMI vector $|\mathbf{D}_{01}|$, respectively. The insets enlarge the torque-fitted regression results for $N_{\text{data}} \leq 100$.

[48]

$$E[\mathbf{m}(\mathbf{r})] = \frac{1}{V} \int_V d\mathbf{r} [A((\nabla m_x)^2 + (\nabla m_y)^2 + (\nabla m_z)^2) + D \mathbf{m} \cdot (\nabla \times \mathbf{m})], \quad (49)$$

where $\mathbf{m}(\mathbf{r}) = (m_x(\mathbf{r}), m_y(\mathbf{r}), m_z(\mathbf{r}))$ is the normalized magnetization field, A is the spin-stiffness constant, and D is the spiralization constant; under cubic symmetry, the anisotropic symmetric exchange term does not contribute to the micromagnetic parameters. The parameters A and D are calculated as [47]

$$A = \frac{1}{2} \sum_{ij} J_{ij} \mathbf{R}_{ij} \cdot \mathbf{R}_{ij}, \quad (50)$$

$$D = \sum_{ij} \mathbf{D}_{ij} \cdot \mathbf{R}_{ij}, \quad (51)$$

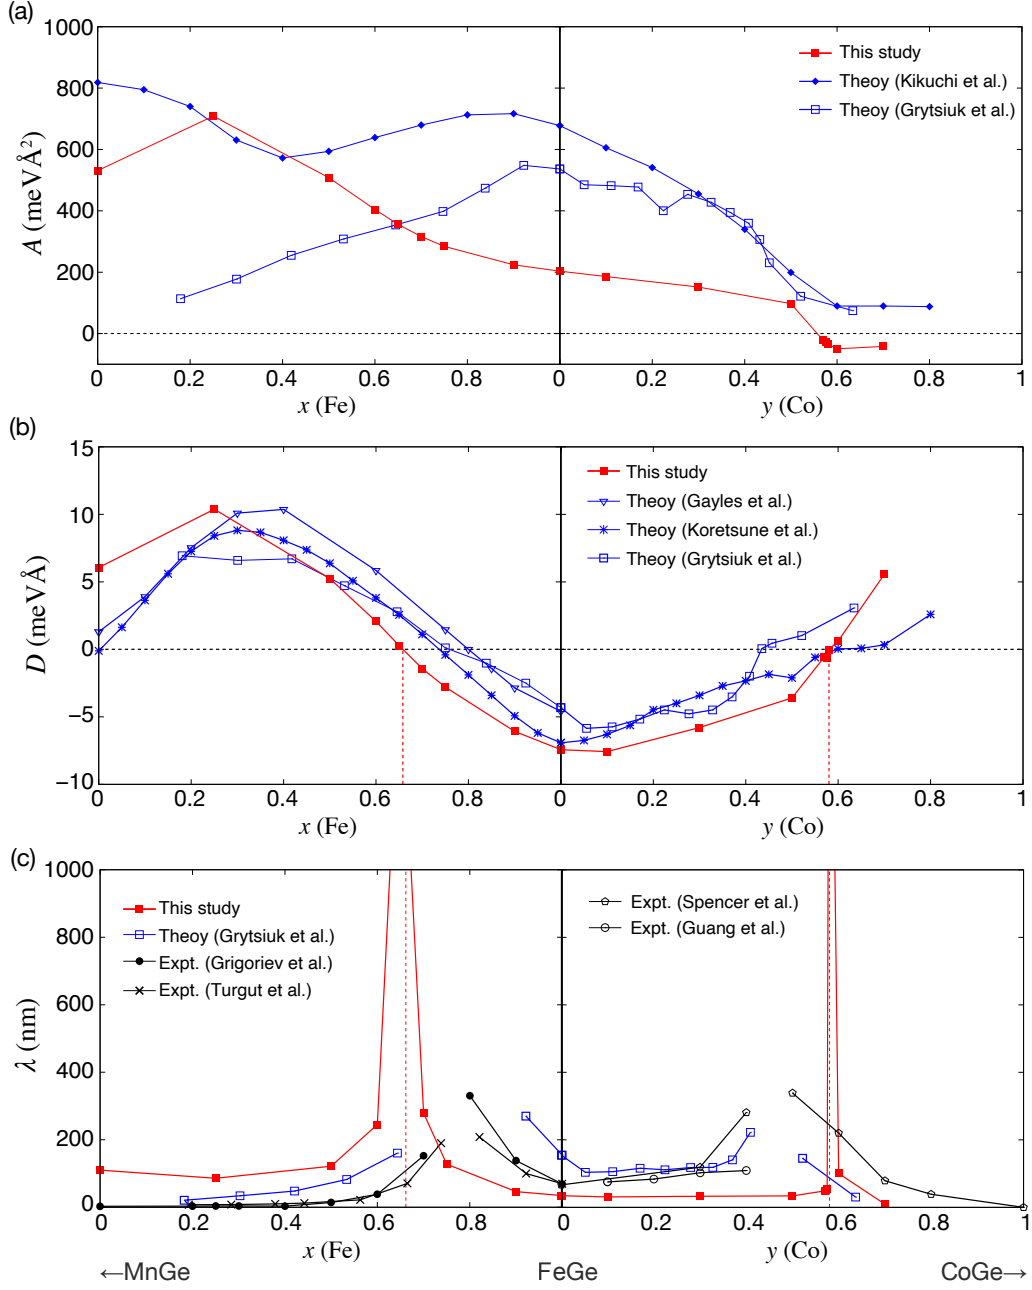


FIG. 3. (a) Spin stiffness constant A , (b) spiralization constant D , and (c) helical spin period λ in $\text{Mn}_{1-x}\text{Fe}_x\text{Ge}$ and $\text{Fe}_{1-y}\text{Co}_y\text{Ge}$. Results of previous theoretical works [44–47] and experimental works [37, 41–43] are also presented for reference.

where $\mathbf{R}_{ij} = \mathbf{R}_j - \mathbf{R}_i$ is the relative vector between atom i and j . The helical period λ then follows as

$$\lambda = 4\pi \left| \frac{A}{D} \right|. \quad (52)$$

The sign of D does not affect λ but sets the handedness (right- or left-handed) of the helix [37]. In the exchange-DMI-only model, λ diverges as $D \rightarrow 0$, corresponding to the ferromagnetic limit.

Figures 3(a)–(c) show the composition dependence of A ,

D , and λ . Here, we emulated changes in chemical composition by electron and hole doping, and the lattice constant was fixed to that of FeGe. The number of data N_{data} is set to 100. For the spin stiffness constant A [Fig. 3(a)], we find sizable deviations from previous theoretical studies [45, 47] across the composition range of $\text{Mn}_{1-x}\text{Fe}_x\text{Ge}$. Given that the experimental magnetic transition temperatures of FeGe and MnGe are ~ 280 K and ~ 170 K, respectively, and that within mean-field theory critical temperature is proportional to A , the results of Grytsiuk *et al.* [47] capture the expected

trend (they evaluated spin-model parameters by a perturbative approach), whereas our data exhibit the opposite tendency. A likely origin is the limited simulation cell used here ($2 \times 2 \times 2$). Indeed, Ref. [12] reports that the nearest-neighbor J_{ij} between Mn atoms in MnGe is roughly twice as large as the nearest-neighbor Fe-Fe J_{ij} in FeGe; nevertheless, the smaller transition temperature of MnGe can be understood as arising from contributions of longer-range J_{ij} . However, within the SCE framework this discrepancy can be systematically reduced by increasing the supercell size; the remaining choice becomes a trade-off between computational cost and accuracy.

Regarding the parameter D [Fig. 3(b)], its composition dependence agrees well with previous theoretical studies. In particular, we find the sign change of D around $x(\text{Fe}) \approx 0.6$ – 0.7 and $y(\text{Co}) \approx 0.6$. As noted above, the helical period λ diverges at compositions where $D = 0$. Figure 3(c) compares λ calculated from A and D as Eq. (52) with experimental results. Experiments likewise show a divergence near $x(\text{Fe}) \approx 0.8$ and $y(\text{Co}) \approx 0.5$; aside from modest offsets, the overall trends are consistent. These offsets are reasonable in light of our computational setup—varying the electron number only while fixing the lattice constant—and fall within the expected uncertainty. Overall, although finite-size effects associated with the supercell used here are present, our calculations clearly indicate that the SCE framework attains systematically improved accuracy as the cell size is increased. In the following, we evaluate the impact of spin fluctuations—a representative temperature effect—where the advantages of SCE become particularly pronounced.

Whether a spin model can accurately capture the impact of thermal magnetic disorder is a key requirement for quantitative modeling. In this regard, the SCE approach offers a complementary advantage to widely used perturbative schemes. Whereas perturbative methods are formulated around infinitesimal spin rotations about a chosen reference state, SCE constructs the spin model directly from datasets of genuinely disordered magnetic configurations. Following the $\tau = 0.1$ results presented above, we increase the reduced temperature to $\tau = 0.3$, sample 100 spin configurations, and construct the corresponding SCE model. We also construct an SCE model with the expansion cutoff in Eq. (47) raised from $l_{\max} = 1$ to $l_{\max} = 2$ as

$$E_{\text{SCE}} = J_0 + \sum_{i \neq j} \sum_{l_i, l_j=1}^{l_{\max}=2} \sum_{m_i=-l_i}^{l_i} \sum_{m_j=-l_j}^{l_j} J_{ij} l_m Z_{l_i m_i}(\hat{e}_i) Z_{l_j m_j}(\hat{e}_j), \quad (53)$$

which, in conventional spin-model language, is equivalent to

$$\begin{aligned} E = & - \sum_{i,j,i \neq j} J_{ij} \hat{e}_i \cdot \hat{e}_j \\ & + \sum_{i,j,i \neq j} D_{ij} \cdot (\hat{e}_i \times \hat{e}_j) \\ & + \sum_{i,j,i \neq j} \hat{e}_i^T \Gamma_{ij} \hat{e}_j \\ & + \sum_{i,j,i \neq j} B_{ij} (\hat{e}_i \cdot \hat{e}_j)^2 \\ & + H_{\text{aniso}}^{(4)}, \end{aligned} \quad (54)$$

where B_{ij} is the isotropic biquadratic interaction parameter and $H_{\text{aniso}}^{(4)}$ collects SOC-induced quartic anisotropic two-spin interactions.

The blue and gray points in Figure 4(a) compare DFT torques with those from the $l_{\max} = 1$ SCE model at $\tau = 0.1$ and $\tau = 0.3$, respectively, with all other settings identical, thereby isolating the effect of increased magnetic disorder. At $\tau = 0.1$, the $l_{\max} = 1$ SCE reproduces the DFT torques closely, whereas its predictive accuracy deteriorates at $\tau = 0.3$. These trends indicate that truncation at $l_{\max} = 1$ is valid at very low temperature range but insufficient at elevated temperature. By contrast, at $\tau = 0.3$, extending the SCE to $l_{\max} = 2$ substantially improves the torque prediction accuracy relative to $l_{\max} = 1$. We attribute the reduced $l_{\max} = 1$ accuracy at $\tau = 0.3$ to the larger spread in the magnetic moment magnitude of Fe, $|\mathbf{M}_{\text{Fe}}|$, as discussed below.

Figure 4(b) shows histograms of $|\mathbf{M}_{\text{Fe}}|$ at $\tau = 0.1$ and $\tau = 0.3$ (Ge moments are negligible compared with Fe and are omitted). The $\tau = 0.3$ distribution is visibly broader than at $\tau = 0.1$, indicating larger dispersion in $|\mathbf{M}_{\text{Fe}}|$. This broad variance in $|\mathbf{M}_{\text{Fe}}|$ is strongly correlated with local magnetic disordering. To quantify short-range order among Fe-Fe pairs, we define for each Fe site i the average relative angle to its first-nearest Fe neighbors,

$$\langle \theta_i \rangle = \frac{1}{N_{1\text{NN}}(i)} \sum_{j \in 1\text{NN}(i)} \arccos(\hat{e}_i \cdot \hat{e}_j), \quad (55)$$

where $1\text{NN}(i)$ is the set of first-nearest Fe neighbors of site i and $N_{1\text{NN}}(i)$ is the number of elements in the set $1\text{NN}(i)$. Figure 4(c) clearly shows that larger $\langle \theta_i \rangle$ leads to the shrinkage of $|\mathbf{M}_{\text{Fe}}|$, i.e., $|\mathbf{M}_{\text{Fe}}|$ strongly depends on local magnetic order. Figure 4(d) presents the $\tau = 0.3$, $l_{\max} = 1$ parity plot with points color-coded by the deviation from the modal Fe moment magnitude at $\tau = 0.3$, $|\mathbf{M}_{\text{Fe}}| - |\mathbf{M}_{\text{Fe}}|_{\text{mode}}$. Taken together, these results indicate that the deterioration of the $l_{\max} = 1$ SCE torque predictions with increasing τ stems from its inability to capture the temperature-dependent spread in local moment magnitudes $|\mathbf{M}_{\text{Fe}}|$ induced by magnetic disordering. Moreover, the improvement of torque predictive accuracy by including higher-order interactions can be understood intuitively from Fig. 4(c); these terms provide the nonlinear angular dependence needed to reproduce the energy and torque for configurations with large relative spin angles behavior that cannot be captured by the low-order $l_{\max} = 1$ model. Indeed, the

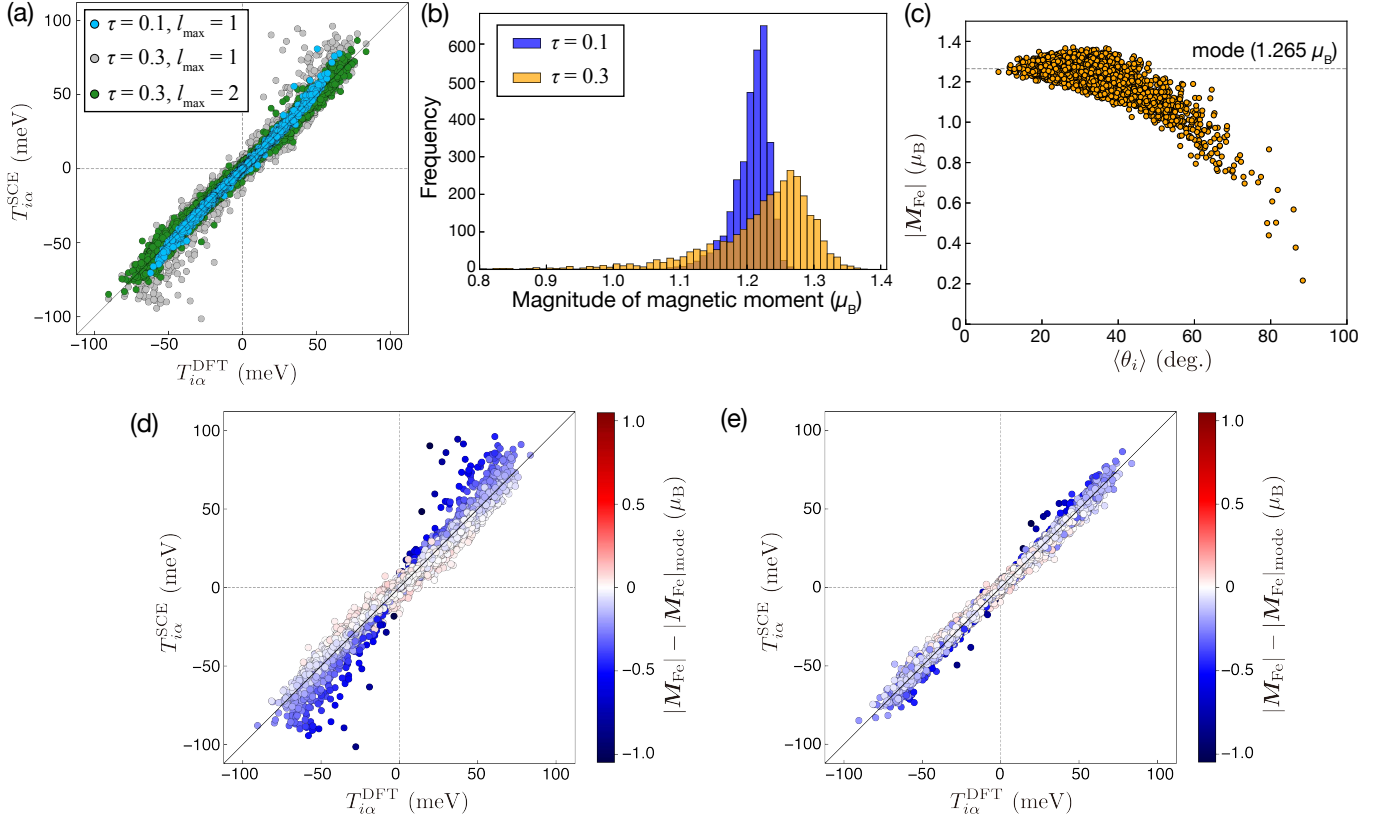


FIG. 4. (a) Parity plot of site-resolved torque components. $x = T_{i\alpha}^{DFT}$, $y = T_{i\alpha}^{SCE}$, $\alpha \in \{x, y, z\}$. (b) Histogram of site-resolved magnetic-moment magnitudes of Fe $|M_{Fe}|$ at $\tau = 0.1$ (blue) and $\tau = 0.3$ (orange); bin width $0.01 \mu_B$. (c) $\langle \theta_i \rangle$ defined in Eq. (55) plotted against Fe moment magnitude $|M_{Fe}|$. (d)(e) Parity plots of Fe torques at $\tau = 0.3$ for $l_{\max} = 1$ and $l_{\max} = 2$, respectively. Points are color-coded by the deviation from the modal Fe moment magnitude, $|M_{Fe}| - |M_{Fe}|_{\text{mode}}$. The modal value is $|M_{Fe}|_{\text{mode}} = 1.265 \mu_B$.

torques on atoms with strongly shrunk local moments—poorly captured by the $l_{\max} = 1$ model [Fig. 4(d)]—are reproduced much more accurately by the $l_{\max} = 2$ SCE model [Fig. 4(e)].

Experimentally, while the helical period λ of FeGe exhibits only weak temperature dependence from a quite low temperature to the critical temperature, the spin-stiffness constant A decreases with increasing temperature [40]. Clearly, this implies that an exchange-DMI-only model, with parameters determined at a single temperature, is insufficient to quantitatively describe magnetic order over a broad temperature range. To address this issue, two approaches can be considered: (i) employ a temperature-dependent exchange-DMI-only model or (ii) construct a spin model that includes higher-order interactions capable of describing a broader temperature range (i.e., a broader spin configuration space). However, as we have shown, the $l_{\max} = 1$ SCE model cannot adequately renormalize the effects of fluctuations in the local-moment magnitude $|M_{Fe}|$; thus, option (ii) is the more appropriate route for capturing magnetism across a wide temperature range. In this context, the advantages of SCE become particularly pronounced: by tuning the model capacity—e.g., increasing l_{\max} and/or the set of included clusters—one can systematically build quantitative spin models. In practice, care must be taken to monitor and mitigate overfitting during model selection. Finally,

we note a conceptual distinction from approaches based on the magnetic force theorem (MFT) [49, 50] when evaluating higher-order interactions [51, 52]. MFT extracts interaction parameters from the energy change under infinitesimal spin rotations about a chosen reference state and uses the variation of the single-particle (band) energy within a frozen potential. By contrast, the SCE method samples finite rotations and fits to quantities obtained from fully self-consistent DFT calculations, thereby reflecting the *total* DFT energy, including band energy and double-counting corrections. Consequently—and provided finite-size effects are adequately controlled—SCE offers a complementary, self-consistent route to estimating higher-order couplings, particularly in regimes with finite rotations or longitudinal fluctuations, and thus serves as a natural counterpart to the MFT analyses.

III. DISCUSSION

We have proposed a supercell-based framework for evaluating magnetic interactions of arbitrary form within SCE. In this approach, diverse spin configurations and their site-resolved magnetic torques are computed by constrained noncollinear-spin DFT and used as training data, enabling a highly efficient

torque-fitted regression for the SCE model. We applied this framework to representative chiral magnet systems, B20-type FeGe and its variants $\text{Mn}_{1-x}\text{Fe}_x\text{Ge}$ and $\text{Fe}_{1-y}\text{Co}_y\text{Ge}$. The computed spiralization constant D agrees with other theoretical studies, and the compositions where the helical period diverges are also correctly reproduced. As a distinctive strength of SCE, we have demonstrated the importance of higher-order interactions in moderately disordered magnetic states of FeGe. At elevated temperature, the Fe magnetic moments exhibit a wide variance around the modal value. As a result, the lowest-order truncation fails to maintain torque predictive accuracy, whereas including higher-order terms restores agreement. The variance of the local moment strongly depends on the local magnetic disorder (i.e., relative spin angles between nearest-neighbor spins), and higher-order interactions play a compensating role when these relative angles become large. Thus, although the SCE model does not include an explicit degree of freedom for the moment magnitude, spin-configuration-dependent changes in the moment length are implicitly captured through higher-order interactions.

A variety of extensions of the SCE framework are conceivable. In this work we preselected a magnetic state of interest and sampled spin configurations in its vicinity; however, because the SCE basis is complete and orthogonal, it can—within the regime where the mapping from spin configuration to energy is single-valued—represent the energies of arbitrary magnetic states. When combined with strategies that efficiently sample a broad manifold of configurations, this should enable quantitative descriptions over wide temperature ranges and high-fidelity predictions of more complex magnetic textures. While the use of supercells increases computational cost, it also enables direct treatments of atomic displacements. Since spin and lattice degrees of freedom can couple strongly (e.g., via lattice vibrations [52–56] and magneto-elastic effects [57–59]), a supercell approach that explicitly displaces atoms offers a route to computing spin–lattice coupling with higher accuracy.

IV. METHODS

A. Constrained noncollinear-spin DFT

For the constrained noncollinear-spin DFT calculations, we used the VASP package [60, 61] with the projector augmented-wave (PAW) method [62] and the generalized-gradient approximation functional of Perdew, Burke, and Ernzerhof (PBE) [63]. The constrained local moment approach [29] was employed to fix the directions of the atomic magnetic moments, while allowing their magnitudes to relax. Spin–orbit coupling was included self-consistently. The electronic energy-convergence threshold was set to 10^{-7} eV/atom. A plane-wave cutoff energy of 300 eV and a $5 \times 5 \times 5$ k -point grid were used for a $2 \times 2 \times 2$ cubic supercell (64 atoms). The lattice constant and internal atomic positions were taken from the experimental values of FeGe reported in Ref. [34]. Atomic radii of 1.242 Å for Fe and 1.161 Å for Ge were used for the constrained local moment calculations.

B. Conversion from the SCE model to a conventional spin model

For the $l = 1$ sector we relabel the real spherical harmonics by Cartesian indices via $Z_{1x} \equiv Z_{11}$, $Z_{1y} \equiv Z_{1\bar{1}}$, and $Z_{1z} \equiv Z_{10}$, and define $\mathbf{Z}_1(\hat{e}_i) \equiv (Z_{1x}(\hat{e}_i), Z_{1y}(\hat{e}_i), Z_{1z}(\hat{e}_i))^T$. Using

$$\sqrt{4\pi/3} \mathbf{Z}_1(\hat{e}_i) = \hat{e}_i,$$

the two-body $l = 1$ contribution of the SCE energy can be written as

$$E_{l=1}^{(2)} = 4\pi \sum_{i,j,i \neq j} \mathbf{Z}_1(\hat{e}_i)^T \mathbf{J}_{ij}^{(1)} \mathbf{Z}_1(\hat{e}_j) \quad (56)$$

$$= 3 \sum_{i,j,i \neq j} \hat{e}_i^T \mathbf{J}_{ij}^{(1)} \hat{e}_j \equiv \sum_{i,j,i \neq j} \hat{e}_i^T \mathcal{J}_{ij} \hat{e}_j, \quad (57)$$

with the identification

$$\mathcal{J}_{ij} = 3 \mathbf{J}_{ij}^{(1)}, \quad \mathbf{J}_{ij}^{(1)} = (J_{ij,\mu\nu}^{(1)})_{\mu,\nu \in \{x,y,z\}}. \quad (58)$$

Thus the conventional exchange tensor \mathcal{J}_{ij} is obtained directly from the $l = 1$ block of the SCE coefficients. Decomposing \mathcal{J}_{ij} into isotropic, symmetric traceless, and antisymmetric parts gives

$$J_{ij} = -\frac{1}{3} \text{tr} \mathcal{J}_{ij}, \quad (59)$$

$$\mathbf{\Gamma}_{ij} = \frac{1}{2} (\mathcal{J}_{ij} + \mathcal{J}_{ij}^T) + J_{ij} \mathbb{I}, \quad (60)$$

$$\mathcal{W}_{ij} = \frac{1}{2} (\mathcal{J}_{ij} - \mathcal{J}_{ij}^T), \quad (61)$$

where \mathbb{I} is the identity matrix. The antisymmetric exchange \mathcal{W}_{ij} is in one-to-one correspondence with the Dzyaloshinskii–Moriya (DMI) vector \mathbf{D}_{ij} . At the component level,

$$\mathcal{W}_{ij}^{\alpha\beta} = \sum_{\gamma} \varepsilon_{\alpha\beta\gamma} D_{ij}^{\gamma}, \quad (62)$$

$$D_{ij}^{\gamma} = \frac{1}{2} \sum_{\alpha\beta} \varepsilon_{\alpha\beta\gamma} \mathcal{W}_{ij}^{\alpha\beta}, \quad (63)$$

so that, combining with $\mathcal{W}_{ij} = \frac{1}{2} (\mathcal{J}_{ij} - \mathcal{J}_{ij}^T)$,

$$D_{ij}^{\gamma} = \frac{1}{4} \sum_{\alpha\beta} \varepsilon_{\alpha\beta\gamma} (\mathcal{J}_{ij}^{\alpha\beta} - \mathcal{J}_{ij}^{\beta\alpha}). \quad (64)$$

In matrix form, Eq. (62) is equivalent to

$$\mathcal{W}_{ij} = \begin{pmatrix} 0 & D_{ij}^z & -D_{ij}^y \\ -D_{ij}^z & 0 & D_{ij}^x \\ D_{ij}^y & -D_{ij}^x & 0 \end{pmatrix}. \quad (65)$$

Moreover, for any vectors \mathbf{a}, \mathbf{b} one has the identity

$$\mathbf{a}^T \mathcal{W}_{ij} \mathbf{b} = \mathbf{D}_{ij} \cdot (\mathbf{a} \times \mathbf{b}), \quad (66)$$

which makes the equivalence of the antisymmetric exchange term $\hat{e}_i^T \mathcal{W}_{ij} \hat{e}_j$ and the DMI form $\mathbf{D}_{ij} \cdot (\hat{e}_i \times \hat{e}_j)$ explicit.

DATA AVAILABILITY

The data supporting the findings of this study are available from the first author, T.T., upon reasonable request.

CODE AVAILABILITY

The methodology and implementation presented in this study are available as an open-source Julia package, *Magesty.jl*,

on the first author's GitHub: <https://github.com/Tomonori-Tanaka/Magesty.jl>.

ACKNOWLEDGMENTS

This work was partly supported by JSPS KAKENHI Grant Number JP24K01144 and MEXT-DXMag Grant Number JP-MXP1122715503. The calculations were partly carried out by using facilities of the Supercomputer Center at the Institute for Solid State Physics, the University of Tokyo, and TSUB-AME4.0 supercomputer at Institute of Science Tokyo.

-
- [1] Hirohata, A. *et al.* Review on spintronics: Principles and device applications. *J. Magn. Magn. Mater.* **509**, 166711 (2020).
 - [2] Bai, L. *et al.* Altermagnetism: Exploring new frontiers in magnetism and spintronics. *Adv. Funct. Mater.* **34** (2024).
 - [3] Hohenberg, P. & Kohn, W. Inhomogeneous electron gas. *Phys. Rev.* **136**, B864–B871 (1964).
 - [4] Kohn, W. & Sham, L. J. Self-consistent equations including exchange and correlation effects. *Phys. Rev.* **140**, A1133–A1138 (1965).
 - [5] Skubic, B., Hellsvik, J., Nordström, L. & Eriksson, O. A method for atomistic spin dynamics simulations: implementation and examples. *J. Phys.: Condens. Matter* **20**, 315203 (2008).
 - [6] Yu. Lavrentiev, M., Nguyen-Manh, D. & Dudarev, S. L. Magnetic cluster expansion model for bcc-fcc transitions in Fe and Fe-Cr alloys. *Phys. Rev. B* **81**, 184202 (2010).
 - [7] Lavrentiev, M. Y., Dudarev, S. L. & Nguyen-Manh, D. Magnetic cluster expansion model for high-temperature magnetic properties of iron and iron-chromium alloys. *J. Appl. Phys.* **109**, 07E123 (2011).
 - [8] Evans, R. F. L. *et al.* Atomistic spin model simulations of magnetic nanomaterials. *J. Phys.: Condens. Matter* **26**, 103202 (2014).
 - [9] Eriksson, O., Bergman, A., Bergqvist, L. & Hellsvik, J. *Atomistic spin dynamics: foundations and applications* (Oxford University Press, Oxford, 2017).
 - [10] Yamada, R. & Mohri, T. Conversion of magnetic freedoms into atomic configurational freedoms within the cluster variation method. *Mater. Trans.* **60**, 915–920 (2019).
 - [11] Tanaka, T. & Gohda, Y. Nonperturbative calculation of exchange coupling parameters. *arXiv [cond-mat.mtrl-sci]* (2024).
 - [12] Mendive-Tapia, E. *et al.* Short period magnetization texture of B20-MnGe explained by thermally fluctuating local moments. *Phys. Rev. B* **103**, 024410 (2021).
 - [13] Gutzeit, M., Haldar, S., Meyer, S. & Heinze, S. Trends of higher-order exchange interactions in transition metal trilayers. *Phys. Rev. B* **104**, 024420 (2021).
 - [14] Pan, W. *et al.* Chiral magnetism in lithium-decorated monolayer CrTe₂: Interplay between dzyaloshinskii-moriya interaction and higher-order interactions. *Phys. Rev. B* **109**, 214405 (2024).
 - [15] Drautz, R. & Fähnle, M. Spin-cluster expansion: Parametrization of the general adiabatic magnetic energy surface with *ab initio* accuracy. *Phys. Rev. B* **69**, 104404 (2004).
 - [16] Drautz, R. & Fähnle, M. Parametrization of the magnetic energy at the atomic level. *Phys. Rev. B* **72**, 212405 (2005).
 - [17] Singer, R., Dietermann, F. & Fähnle, M. Spin interactions in bcc and fcc Fe beyond the heisenberg model. *Phys. Rev. Lett.* **107**, 017204 (2011).
 - [18] Connolly, J. W. D. & Williams, A. R. Density-functional theory applied to phase transformations in transition-metal alloys. *Phys. Rev. B* **27**, 5169–5172 (1983).
 - [19] Parlinski, K., Li, Z. Q. & Kawazoe, Y. First-principles determination of the soft mode in cubic ZrO₂. *Phys. Rev. Lett.* **78**, 4063–4066 (1997).
 - [20] Tadano, T., Gohda, Y. & Tsuneyuki, S. Anharmonic force constants extracted from first-principles molecular dynamics: applications to heat transfer simulations. *J. Phys.: Condens. Matter* **26**, 225402 (2014).
 - [21] Unke, O. T. *et al.* Machine learning force fields. *Chem. Rev.* **121**, 10142–10186 (2021).
 - [22] Dederichs, P. H., Blügel, S., Zeller, R. & Akai, H. Ground states of constrained systems: Application to cerium impurities. *Phys. Rev. Lett.* **53**, 2512–2515 (1984).
 - [23] Brinker, S., Dias, M. d. S. & Lounis, S. The chiral biquadratic pair interaction. *New J. Phys.* **21**, 083015 (2019).
 - [24] Jacobsson, A. *et al.* Efficient parameterisation of non-collinear energy landscapes in itinerant magnets. *Sci. Rep.* **12**, 18987 (2022).
 - [25] Rinaldi, M., Mrovec, M., Bochkarev, A., Lysogorskiy, Y. & Drautz, R. Non-collinear magnetic atomic cluster expansion for iron. *npj Comput. Mater.* **10**, 1–12 (2024).
 - [26] Singer, R. & Fähnle, M. Construction of basis functions for the spin-cluster expansion of the magnetic energy on the atomic scale in rotationally invariant systems. *J. Math. Phys.* **47**, 113503 (2006).
 - [27] Dietermann, F., Singer, R. & Fähnle, M. Construction of basis functions with crystal symmetry for the spin-cluster expansion of the magnetic energy on the atomic scale. *J. Math. Phys.* **52**, 123507 (2011).
 - [28] Blanco, M. A., Flórez, M. & Bermejo, M. Evaluation of the rotation matrices in the basis of real spherical harmonics. *J. Mol. Struct. THEOCHEM* **419**, 19–27 (1997).
 - [29] Ma, P.-W. & Dudarev, S. L. Constrained density functional for noncollinear magnetism. *Phys. Rev. B* **91**, 054420 (2015).
 - [30] Drautz, R. Atomic cluster expansion of scalar, vectorial, and tensorial properties including magnetism and charge transfer. *Phys. Rev. B* **102**, 024104 (2020).
 - [31] Györffy, B. L., Pindor, A. J., Staunton, J., Stocks, G. M. & Winter, H. A first-principles theory of ferromagnetic phase transitions in metals. *J. Phys. F: Met. Phys.* **15**, 1337–1386 (1985).
 - [32] Mendive-Tapia, E., Neugebauer, J. & Hickel, T. *Ab initio* calculation of the magnetic Gibbs free energy of materials using

- magnetically constrained supercells. *Phys. Rev. B* **105**, 064425 (2022).
- [33] Ludgren, L., Beckman, O., Attia, V., Bhattacharjee, S. P. & Richardson, M. Helical spin arrangement in cubic FeGe. *Phys. Scr.* **1**, 69–72 (1970).
- [34] Lebech, B., Bernhard, J. & Freltoft, T. Magnetic structures of cubic FeGe studied by small-angle neutron scattering. *J. Phys.: Condens. Matter* **1**, 6105–6122 (1989).
- [35] Kanazawa, N. *et al.* Large topological hall effect in a short-period helimagnet MnGe. *Phys. Rev. Lett.* **106**, 156603 (2011).
- [36] Yu, X. Z. *et al.* Near room-temperature formation of a skyrmion crystal in thin-films of the helimagnet FeGe. *Nature Mater.* **10**, 106–109 (2011).
- [37] Grigoriev, S. V. *et al.* Chiral properties of structure and magnetism in $\text{Mn}_{1-x}\text{Fe}_x\text{Ge}$ compounds: when the left and the right are fighting, who wins? *Phys. Rev. Lett.* **110**, 207201 (2013).
- [38] Shibata, K. *et al.* Towards control of the size and helicity of skyrmions in helimagnetic alloys by spin-orbit coupling. *Nature Nanotech.* **8**, 723–728 (2013).
- [39] Kanazawa, N., Shibata, K. & Tokura, Y. Variation of spin-orbit coupling and related properties in skyrmionic system $\text{Mn}_{1-x}\text{Fe}_x\text{Ge}$. *New J. Phys.* **18**, 045006 (2016).
- [40] Siegfried, S.-A. *et al.* Spin-wave dynamics in the helimagnet FeGe studied by small-angle neutron scattering. *Phys. Rev. B* **95**, 134415 (2017).
- [41] Spencer, C. S. *et al.* Helical magnetic structure and the anomalous and topological Hall effects in epitaxial B20 $\text{Fe}_{1-y}\text{Co}_y\text{Ge}$ films. *Phys. Rev. B* **97**, 214406 (2018).
- [42] Turgut, E. *et al.* Engineering Dzyaloshinskii-Moriya interaction in B20 thin-film chiral magnets. *Phys. Rev. Mater.* **2**, 074404 (2018).
- [43] Guang, Y. *et al.* Topological stability of spin textures in Si/Co-doped helimagnet FeGe. *JPhys Mater.* **7**, 025009 (2024).
- [44] Gayles, J. *et al.* Dzyaloshinskii-Moriya interaction and Hall effects in the Skyrmion phase of $\text{Mn}_{1-x}\text{Fe}_x\text{Ge}$. *Phys. Rev. Lett.* **115**, 036602 (2015).
- [45] Kikuchi, T., Koretsune, T., Arita, R. & Tatara, G. Dzyaloshinskii-Moriya interaction as a consequence of a Doppler shift due to spin-orbit-induced intrinsic spin current. *Phys. Rev. Lett.* **116**, 247201 (2016).
- [46] Koretsune, T., Kikuchi, T. & Arita, R. First-Principles Evaluation of the Dzyaloshinskii-Moriya Interaction. *J. Phys. Soc. Jpn.* (2018).
- [47] Grytsiuk, S. *et al.* *Ab initio* analysis of magnetic properties of the prototype B20 chiral magnet FeGe. *Phys. Rev. B* **100**, 214406 (2019).
- [48] Bornemann, M. *et al.* Complex magnetism of B20-MnGe: from spin-spirals, hedgehogs to monopoles. *J. Phys. Condens. Matter* **31**, 485801 (2019).
- [49] Oguchi, T., Terakura, K. & Hamada, N. Magnetism of iron above the Curie temperature. *J. Phys. F* **13**, 145–160 (1983).
- [50] Liechtenstein, A. I., Katsnelson, M. I., Antropov, V. P. & Gubanov, V. A. Local spin density functional approach to the theory of exchange interactions in ferromagnetic metals and alloys. *J. Magn. Magn. Mater.* **67**, 65–74 (1987).
- [51] Lounis, S. Multiple-scattering approach for multi-spin chiral magnetic interactions: application to the one- and two-dimensional Rashba electron gas. *New J. Phys.* **22**, 103003 (2020).
- [52] Mankovsky, S., Polesya, S. & Ebert, H. Extension of the standard Heisenberg Hamiltonian to multispin exchange interactions. *Phys. Rev. B* **101**, 174401 (2020).
- [53] Ruban, A. V. & Peil, O. E. Impact of thermal atomic displacements on the Curie temperature of 3d transition metals. *Phys. Rev. B* **97**, 174426 (2018).
- [54] Mauger, L. *et al.* Nonharmonic phonons in α -iron at high temperatures. *Phys. Rev. B* **90**, 064303 (2014).
- [55] Tanaka, T. & Gohda, Y. Prediction of the Curie temperature considering the dependence of the phonon free energy on magnetic states. *npj Comput. Mater.* **6**, 184 (2020).
- [56] Tanaka, T. & Gohda, Y. First-principles study of magnetism-dependent phonons governed by exchange ligand field. *J. Phys. Soc. Jpn.* **89**, 093705 (2020).
- [57] Lu, X. Z., Wu, X. & Xiang, H. J. General microscopic model of magnetoelastic coupling from first principles. *Phys. Rev. B* **91**, 100405 (2015).
- [58] Mankovsky, S., Lange, H., Polesya, S. & Ebert, H. Spin-lattice interaction parameters from first principles: Theory and implementation. *Phys. Rev. B* **107**, 144428 (2023).
- [59] Miranda, I. P. *et al.* Spin-lattice couplings in 3d ferromagnets: Analysis from first principles. *Phys. Rev. Mater.* **9**, 024409 (2025).
- [60] Kresse, G. & Furthmüller, J. Efficient iterative schemes for *ab initio* total-energy calculations using a plane-wave basis set. *Phys. Rev. B* **54**, 11169–11186 (1996).
- [61] Kresse, G. & Joubert, D. From ultrasoft pseudopotentials to the projector augmented-wave method. *Phys. Rev. B* **59**, 1758–1775 (1999).
- [62] Blöchl, P. E. Projector augmented-wave method. *Phys. Rev. B* **50**, 17953–17979 (1994).
- [63] Perdew, J. P., Burke, K. & Ernzerhof, M. Generalized gradient approximation made simple. *Phys. Rev. Lett.* **77**, 3865–3868 (1996).

Supplementary Information:

General spin models from noncollinear spin density functional theory and spin-cluster expansion

Tomonori Tanaka* and Yoshihiro Gohda†

Department of Materials Science and Engineering, Institute of Science Tokyo, Yokohama 226-8501, Japan

(Dated: December 5, 2025)

Real spherical harmonics in the Cartesian coordinates

Here we summarize the derivation of the Cartesian forms of the real spherical harmonics and their derivatives. The real spherical harmonics Z_{lm} are defined in terms of the complex Y_{lm} as

$$Z_{lm} = \begin{cases} \frac{(-1)^m}{\sqrt{2}}(Y_{lm} + (-1)^m Y_{l\bar{m}}), & m > 0, \\ Y_{l0}, & m = 0, \\ \frac{(-1)^m}{i\sqrt{2}}(Y_{l|m|} - (-1)^{|m|} Y_{l|\bar{m}|}), & m < 0, \end{cases} \quad (1)$$

and the Cartesian form of the complex spherical harmonics Y_{lm} for $m \geq 0$ is [1]

$$Y_{lm}(\hat{e}_i) = (e_{ix} + ie_{iy})^m \bar{P}_{lm}(e_{iz}), \quad (2)$$

$$\bar{P}_{lm}(e_{iz}) = (-1)^m \sqrt{\frac{2l+1}{4\pi}} \cdot \frac{(l-m)!}{(l+m)!} \frac{d^m}{de_{iz}^m} P_l(e_{iz}), \quad (3)$$

where $\bar{m} \equiv -m$ and $|\bar{m}| \equiv -|m|$. For $m < 0$, the corresponding expressions follow from the relation $Y_{l\bar{m}} = (-1)^{|m|} Y_{l|m|}^*$.

For $m > 0$, suppressing the site index and writing (e_x, e_y, e_z) for the Cartesian components,

$$Z_{lm} = \frac{(-1)^m}{\sqrt{2}} (Y_{lm} + (-1)^m Y_{l\bar{m}}) \quad (4)$$

$$= \frac{(-1)^m}{\sqrt{2}} (Y_{lm} + Y_{lm}^*) \quad (5)$$

$$= \frac{(-1)^m}{\sqrt{2}} \bar{P}_{lm}(e_z) \{ (e_x + ie_y)^m + (e_x - ie_y)^m \} \quad (6)$$

$$= \frac{(-1)^m}{\sqrt{2}} \bar{P}_{lm}(e_z) \sum_{k=0}^m \binom{m}{k} e_x^{m-k} e_y^k (i^k + (-i)^k) \quad (7)$$

$$= (-1)^m \sqrt{2} \bar{P}_{lm}(e_z) \sum_{k=0}^{[m/2]} (-1)^k \binom{m}{2k} e_x^{m-2k} e_y^{2k}, \quad (8)$$

where $[x]$ denotes the floor function (i.e., the largest integer less than or equal to x), and $\binom{m}{k}$ is the binomial coefficient. Similarly, for $m < 0$,

$$Z_{lm} = \frac{(-1)^m}{i\sqrt{2}} (Y_{l|m|} - (-1)^{|m|} Y_{l|\bar{m}|}) \quad (9)$$

$$= \frac{(-1)^m}{i\sqrt{2}} (Y_{l|m|} - Y_{l|m|}^*) \quad (10)$$

$$= (-1)^m \sqrt{2} \bar{P}_{l|m|}(e_z) \sum_{k=0}^{[(|m|-1)/2]} (-1)^k \binom{|m|}{2k+1} e_x^{|m|-(2k+1)} e_y^{2k+1}. \quad (11)$$

* tanaka.t.da74@m.isct.ac.jp

† gohda@mct.isct.ac.jp

For $m = 0$,

$$Z_{l0} = Y_{l0} = \bar{P}_{l0}(e_z). \quad (12)$$

In the above derivations we used the identities

$$i^k + (-i)^k = \begin{cases} 0 & \text{if } k \text{ is odd} \\ 2(-1)^{k/2} & \text{if } k \text{ is even} \end{cases}, \quad (13)$$

$$i^k - (-i)^k = \begin{cases} 2i(-1)^{(k+1)/2} & \text{if } k \text{ is odd} \\ 0 & \text{if } k \text{ is even} \end{cases}. \quad (14)$$

The Cartesian derivatives then follow directly. For $m > 0$,

$$\frac{\partial Z_{lm}}{\partial e_x} = \frac{(-1)^m}{\sqrt{2}} \left(\frac{\partial Y_{lm}}{\partial e_x} + \frac{\partial Y_{lm}^*}{\partial e_x} \right) \quad (15)$$

$$= \frac{(-1)^m}{\sqrt{2}} \bar{P}_{lm}(e_z) [m(e_x + ie_y)^{m-1} + m(e_x - ie_y)^{m-1}] \quad (16)$$

$$= \frac{(-1)^m}{\sqrt{2}} m \bar{P}_{lm}(e_z) \sum_{k=0}^{m-1} \binom{m-1}{k} e_x^{m-1-k} e_y^k (i^k + (-i)^k) \quad (17)$$

$$= (-1)^m \sqrt{2} m \bar{P}_{lm}(e_z) \sum_{k=0}^{[(m-1)/2]} (-1)^k \binom{m-1}{2k} e_x^{m-1-2k} e_y^{2k}, \quad (18)$$

$$\frac{\partial Z_{lm}}{\partial e_y} = \frac{(-1)^m}{\sqrt{2}} \left(\frac{\partial Y_{lm}}{\partial e_y} + \frac{\partial Y_{lm}^*}{\partial e_y} \right) \quad (19)$$

$$= \frac{(-1)^m}{\sqrt{2}} \bar{P}_{lm}(e_z) [im(e_x + ie_y)^{m-1} - im(e_x - ie_y)^{m-1}] \quad (20)$$

$$= \frac{(-1)^m}{\sqrt{2}} im \bar{P}_{lm}(e_z) \sum_{k=0}^{m-1} \binom{m-1}{k} e_x^{m-1-k} e_y^k (i^k - (-i)^k), \quad (21)$$

$$= (-1)^{m+1} \sqrt{2} m \bar{P}_{lm}(e_z) \sum_{k=0}^{[(m-2)/2]} (-1)^k \binom{m-1}{2k+1} e_x^{m-2-2k} e_y^{2k+1} \quad (22)$$

$$\frac{\partial Z_{lm}}{\partial e_z} = (-1)^m \sqrt{2} \left(\frac{d\bar{P}_{lm}(e_z)}{de_z} \right) \sum_{k=0}^{[m/2]} (-1)^k \binom{m}{2k} e_x^{m-2k} e_y^{2k}. \quad (23)$$

For $m = 0$,

$$\frac{\partial Z_{l0}}{\partial e_x} = 0, \quad (24)$$

$$\frac{\partial Z_{l0}}{\partial e_y} = 0, \quad (25)$$

$$\frac{\partial Z_{l0}}{\partial e_z} = \frac{d\bar{P}_{l0}(e_z)}{de_z}. \quad (26)$$

For $m < 0$,

$$\frac{\partial Z_{lm}}{\partial e_x} = \frac{(-1)^m}{i\sqrt{2}} \left(\frac{\partial Y_{l|m|}}{\partial e_x} - \frac{\partial Y_{l|\overline{m}|}}{\partial e_x} \right) \quad (27)$$

$$= \frac{(-1)^m}{i\sqrt{2}} \bar{P}_{l|m|}(e_z) \left[|m|(e_x + ie_y)^{|m|-1} - |m|(e_x - ie_y)^{|m|-1} \right] \quad (28)$$

$$= \frac{(-1)^m}{i\sqrt{2}} |m| \bar{P}_{l|m|}(e_z) \sum_{k=0}^{|m|-1} \binom{|m|-1}{k} e_x^{|m|-1-k} e_y^k (i^k - (-i)^k) \quad (29)$$

$$= (-1)^m \sqrt{2} |m| \bar{P}_{l|m|}(e_z) \sum_{k=0}^{[(|m|-2)/2]} (-1)^k \binom{|m|-1}{2k+1} e_x^{|m|-2-2k} e_y^{2k+1}, \quad (30)$$

$$\frac{\partial Z_{lm}}{\partial e_y} = \frac{(-1)^m}{i\sqrt{2}} \left(\frac{\partial Y_{l|m|}}{\partial e_y} - \frac{\partial Y_{l|\overline{m}|}}{\partial e_y} \right) \quad (31)$$

$$= \frac{(-1)^m}{\sqrt{2}} |m| \bar{P}_{l|m|}(e_z) \sum_{k=0}^{|m|-1} \binom{|m|-1}{k} e_x^{|m|-1-k} e_y^k (i^k + (-i)^k) \quad (32)$$

$$= (-1)^m \sqrt{2} |m| \bar{P}_{l|m|}(e_z) \sum_{k=0}^{[(|m|-1)/2]} (-1)^k \binom{|m|-1}{2k} e_x^{|m|-1-2k} e_y^{2k} \quad (33)$$

$$\frac{\partial Z_{lm}}{\partial e_z} = (-1)^m \sqrt{2} \left(\frac{d\bar{P}_{l|m|}(e_z)}{de_z} \right) \sum_{k=0}^{[(|m|-1)/2]} (-1)^k \binom{|m|}{2k+1} e_x^{|m|-2k-1} e_y^{2k+1}. \quad (34)$$

- [1] Drautz, R. Atomic cluster expansion of scalar, vectorial, and tensorial properties including magnetism and charge transfer. *Phys. Rev. B* **102**, 024104 (2020).